Bending, Vibration and Buckling of Laminated Composite Plates Using a Simple Four Variable Plate Theory

Abstract

In the present study, a simple trigonometric shear deformation theory is applied for the bending, buckling and free vibration of cross-ply laminated composite plates. The theory involves four unknown variables which are five in first order shear deformation theory or any other higher order theories. The in-plane displacement field uses sinusoidal function in terms of thickness co-ordinate to include the shear deformation effect. The transverse displacement includes bending and shear components. The present theory satisfies the zero shear stress conditions at top and bottom surfaces of plates without using shear correction factor. Equations of motion associated with the present theory are obtained using the dynamic version of virtual work principle. A closed form solution is obtained using double trigonometric series suggested by Navier. The displacements, stresses, critical buckling loads and natural frequencies obtained using present theory are compared with previously published results and found to agree well with those.

Atteshamuddin S. Sayyad [a]
Bharti M. Shinde [a]
Yuwaraj M. Ghugal [b]

[a] Department of Civil Engineering, SRES's College of Engineering, Savitribai Phule Pune University, Kopargaon-423601, M.S., India
Email: attu_sayyad@yahoo.co.in
Email: bhartishinde1987@yahoo.co.in

[b] Department of Applied Mechanics, Government Engineering College, Karad-415124, M.S., India
Email: ghugal@rediffmail.com

NOMENCLATURE

x, y, z Cartesian co-ordinates

a, b, h Length, width and thickness of plate respectively

N Number of layers

h_k Thickness ordinate of k^{th} layer

u, v, w Displacements in x, y, z direction respectively

u_0, v_0 Displacement of mid-plane ($z = 0$) in x and y direction respectively

u_b, u_s Bending and shear components of displacement in x- direction

v_b, v_s Bending and shear components of displacement in y- direction

NOMENCLATURE (continuation)

w_b, w_s	Bending and Shear components of transverse displacement respectively
ε_x, ε_y	Normal Strains
$\gamma_{xy}, \gamma_{xz}, \gamma_{yz}$	Shear Strains
σ_x, σ_y	In-plane normal Stresses
$\tau_{xy}, \tau_{xz}, \tau_{yz}$	Shear stresses
E_1, E_2	Young's moduli along and transverse directions of the fibre
G_{12}, G_{13}, G_{23}	In-plane and transverse shear moduli
μ_{12}, μ_{21}	Poisson's ratios
δ	Variational operator
Q_{ij}	Plane stress reduced elastic constants
$q(x, y)$	Transverse load
q_{mn}	Coefficient of Fourier expansion
q_0	Maximum intensity of transverse load at the centre of plate
$[K]$	Stiffness matrix
ρ	Density of material
ω	Natural frequency
$N_{xx}^0, N_{yy}^0, N_{xy}^0$	In-plane compressive forces
N_0	Maximum intensity of in-plane compressive forces
$\overline{u}, \overline{v}, \overline{w}$	Non-dimensional displacements
$\overline{\sigma}_x, \overline{\sigma}_y$	Non-dimensional in-plane normal stresses
$\overline{\tau}_{xy}, \overline{\tau}_{xz}, \overline{\tau}_{yz}$	Non-dimensional shear stresses
$\overline{\omega}$	Non-dimensional frequency
N_{cr}	Critical buckling load

1 INTRODUCTION

Since the composite materials are increasingly being used in many engineering applications due to their attractive properties, such as stiffness, strength, weight reduction, corrosion resistance, thermal properties, fatigue life, and wear resistance. The plates made up of such materials are required accurate structural analysis to predict the correct bending behaviour.

The effect of transverse shear deformation is more significant in thick plates than in thin plates. Therefore, various plate theories have been developed by researchers to predict correct bending behaviour of thick plates. The classical plate theory (CPT) of Kirchhoff (1850) is not suitable for thick plate due to neglect of transverse shear deformation. The first order shear deformation theory (FSDT) developed by Mindlin (1951) is also not suitable for the analysis since it does not satisfy the zero stress conditions at top and bottom surfaces of the plate and required problem dependent shear correction factors. Therefore, many five variable and six variable plate theories have been developed for the analysis of plates (Reddy, 1984; Touratier, 1991; Soldatos, 1992; Karama et al., 2009; Sayyad

and Ghugal, 2012; Sayyad, 2013; Zenkour, 2006; Sayyad and Ghugal, 2013; 2014a; 2014b; Ghugal and Sayyad, 2010; 2013a; 2013b; Metin, 2009).

In the last decade, a new class of plate theories has been developed by researchers in which displacement field involves only four unknowns. Shimpi and Patel (2006) were the first to present a plate theory involving two unknowns for bending and free vibration analysis of orthotropic plates. This theory is further extended by Thai and Kim (2010) for the free vibration analysis of cross-ply and angle-ply laminated plates considering four and five unknowns. Kim et al. (2009) also used this theory for the buckling analysis of orthotropic plates using the Navier solution technique. Thai and Kim (2011; 2012) employed Levy type solution for the bending and buckling analysis of orthotropic plates. After this, a lot of research is reported in the literature on different four variable plate theories. However, these theories are applied for bending, buckling and free vibration analysis of functionally graded plates only (Ameur, et al. 2011; Thai and Vo, 2013; Meiche et al., 2011; Daouadji et al., 2012; 2013; Zenkour, 2013). Recently Sayyad and Ghugal (2015) have presented a critical review of literature on refined shear deformation theories for the free vibration analysis of laminated composite and sandwich plates. Wherein, theories involving four or more than four are reviewed and discussed.

In the present study, an attempt is made to check the efficiency of four variable refined trigonometric shear deformation theory for the bending, buckling and free vibration analysis of cross-ply laminated composite plates. A trigonometric function in terms of thickness co-ordinate is used in the kinematics of the theory to account for shear deformation effects. The theory enforces cosine distribution of transverse shear stresses and satisfies zero shear stress conditions at top and bottom surfaces of the plates. The theory does not need problem dependent shear correction factor. Governing equations and boundary conditions are obtained using the virtual work principle. A closed form solution is obtained by employing a double trigonometric series technique developed by Navier. Finally, the numerical results obtained by using present theory are compared with exact elasticity solutions given by Pagano (1970) for bending, Noor (1973) for free vibration and Noor (1975) for buckling analysis of laminated composite plates.

2 MATHEMATICAL FORMULATION

2.1 Laminated Plate Under Consideration

A rectangular plate of the sides 'a' and 'b' and total thickness 'h' as shown in Figure 1 is considered. The plate consists of N number of homogenous layers. All the layers are perfectly bounded together and made up of linearly elastic and orthotropic material. The plate occupies the region $0 \leq x \leq a$, $0 \leq y \leq b$, $-h/2 \leq z \leq h/2$ in Cartesian coordinate system. The downward z-direction is taken as positive. The plate is subjected to transverse load $q(x, y)$ on the upper surface of the plate (*i.e.* $z = -h/2$) or subjected to in-plane compressive forces (uniaxial/biaxial).
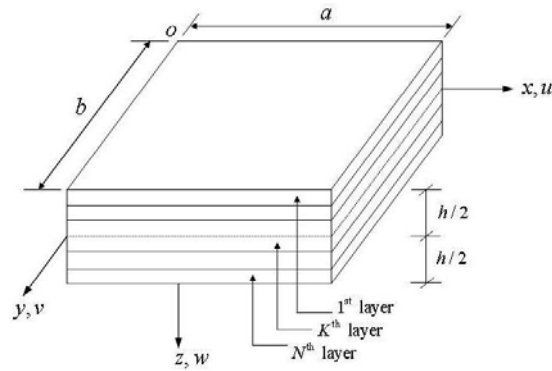
Figure 1: Geometry and co-ordinate system of laminated plate.

2.2 Assumptions Made in Mathematical Formulation.

Mathematical formulation of the present theory is based on the following assumptions.

1. The displacements are small in comparison with the plate thickness and, therefore, strains involved are infinitesimal.
2. The displacements u in x-direction and v in y-direction consist of extension (u_0), bending (u_b) and shear components (u_s).

$$u = u_0 + u_b + u_s \quad \text{and} \quad v = v_0 + v_b + v_s \tag{1}$$

3. The transverse displacement w includes two components, *i.e.* bending $\left(w_b\right)$ and shear $\left(w_s\right)$

$$w = w_b + w_s \tag{2}$$

2.3 Kinematics and Constitutive Relations

Based on the before mentioned assumptions the following displacement field associated with present theory is obtained.

$$u(x,y,z,t) = u_0(x,y,t) - z\frac{\partial w_b(x,y,t)}{\partial x} - \left(z - \frac{h}{\pi}\sin\frac{\pi z}{h}\right)\frac{\partial w_s(x,y,t)}{\partial x}$$

$$v(x,y,z,t) = v_0(x,y,t) - z\frac{\partial w_b(x,y,t)}{\partial y} - \left(z - \frac{h}{\pi}\sin\frac{\pi z}{h}\right)\frac{\partial w_s(x,y,t)}{\partial y} \tag{3}$$

$$w(x,y,t) = w_b(x,y,t) + w_s(x,y,t)$$

The non-zero normal and shear strain components are obtained using strain displacement relations given by Jones (1975).

$$\left\{\begin{array}{c}\varepsilon_x \\ \varepsilon_y \\ \gamma_{xy}\end{array}\right\} = \left\{\begin{array}{c}\dfrac{\partial u}{\partial x} \\[6pt] \dfrac{\partial v}{\partial y} \\[6pt] \dfrac{\partial u}{\partial y}+\dfrac{\partial v}{\partial x}\end{array}\right\} = \left\{\begin{array}{c}\dfrac{\partial u_0}{\partial x} \\[6pt] \dfrac{\partial v_0}{\partial y} \\[6pt] \dfrac{\partial u_0}{\partial y}+\dfrac{\partial v_0}{\partial x}\end{array}\right\} - z\left\{\begin{array}{c}\dfrac{\partial^2 w_b}{\partial x^2} \\[6pt] \dfrac{\partial^2 w_b}{\partial y^2} \\[6pt] 2\dfrac{\partial^2 w_b}{\partial x\,\partial y}\end{array}\right\} - \left(z-\dfrac{h}{\pi}\sin\dfrac{\pi z}{h}\right)\left\{\begin{array}{c}\dfrac{\partial^2 w_s}{\partial x^2} \\[6pt] \dfrac{\partial^2 w_s}{\partial y^2} \\[6pt] 2\dfrac{\partial^2 w_s}{\partial x\,\partial y}\end{array}\right\} \tag{4}$$

$$\left\{\begin{array}{c}\gamma_{yz} \\ \gamma_{xz}\end{array}\right\} = \left\{\begin{array}{c}\dfrac{\partial v}{\partial z}+\dfrac{\partial w}{\partial y} \\[6pt] \dfrac{\partial u}{\partial z}+\dfrac{\partial w}{\partial x}\end{array}\right\} = \cos\dfrac{\pi z}{h}\left\{\begin{array}{c}\dfrac{\partial w_s}{\partial y} \\[6pt] \dfrac{\partial w_s}{\partial x}\end{array}\right\}$$

The constitutive relationships for the k^{th} layer can be given as,

$$\left\{\begin{array}{c}\sigma_x \\ \sigma_y \\ \tau_{xy}\end{array}\right\}^k = \left[\begin{array}{ccc}Q_{11} & Q_{12} & 0 \\ Q_{12} & Q_{22} & 0 \\ 0 & 0 & Q_{66}\end{array}\right]^k \left\{\begin{array}{c}\varepsilon_x \\ \varepsilon_y \\ \gamma_{xy}\end{array}\right\}^k \quad \text{and} \quad \left\{\begin{array}{c}\tau_{yz} \\ \tau_{xz}\end{array}\right\}^k = \left[\begin{array}{cc}Q_{44} & 0 \\ 0 & Q_{55}\end{array}\right]^k \left\{\begin{array}{c}\gamma_{yz} \\ \gamma_{xz}\end{array}\right\}^k \tag{5}$$

where Q_{ij} are the plane stress reduced elastic constants in the material axes of the plate, and are defined as:

$$Q_{11} = \frac{E_1}{1-\mu_{12}\mu_{21}}, \ Q_{12} = \frac{\mu_{12}E_2}{1-\mu_{12}\mu_{21}}, \ Q_{22} = \frac{E_2}{1-\mu_{12}\mu_{21}}, \ Q_{66} = G_{12}, \ Q_{55} = G_{13}, \ Q_{44} = G_{23} \tag{6}$$

where E_1, E_2 are the Young's moduli along and transverse direction of the fibre, G_{12}, G_{13}, G_{23} are the in-plane and transverse shear moduli and μ_{12}, μ_{21} are the Poisson's ratios. The force and moment resultants of a present theory can be obtained by integrating stresses given by Eq. (5) through the thickness and are as follows:

$$\left\{\begin{array}{c}N_x \\ N_y \\ N_{xy}\end{array}\right\} = \sum_{k=1}^{N}\int_{-h/2}^{h_k}\left\{\begin{array}{c}\sigma_x \\ \sigma_y \\ \tau_{xy}\end{array}\right\}dz; \quad \left\{\begin{array}{c}M_x^b \\ M_y^b \\ M_{xy}^b\end{array}\right\} = \sum_{k=1}^{N}\int_{-h/2}^{h_k}\left\{\begin{array}{c}\sigma_x \\ \sigma_y \\ \tau_{xy}\end{array}\right\}z\,dz;$$

$$\left\{\begin{array}{c}M_x^s \\ M_y^s \\ M_{xy}^s\end{array}\right\} = \sum_{k=1}^{N}\int_{-h/2}^{h_k}\left\{\begin{array}{c}\sigma_x \\ \sigma_y \\ \tau_{xy}\end{array}\right\}f(z)\,dz; \quad \left\{\begin{array}{c}Q_x \\ Q_y\end{array}\right\} = \sum_{k=1}^{N}\int_{-h/2}^{h_k}\left\{\begin{array}{c}\tau_{xz} \\ \tau_{yz}\end{array}\right\}g(z)\,dz \tag{7}$$

where h_k is the thickness ordinate of k^{th} layer. The terms $\left(N_x, N_y, N_{xy}\right)$ and $\left(M_x^b, M_y^b, M_{xy}^b\right)$ are the in-plane force and moment resultants associated with the classical plate theory whereas, $\left(Q_x, Q_y\right)$ and

$\left(M_x^s, M_y^s, M_{xy}^s \right)$ are the transverse shear force and moment resultants associated with the transverse shear deformation.

3 EQUATIONS OF MOTION

The variationally consistent governing equations of motion and boundary conditions associated with the present theory can be derived using the principle of virtual work. The analytical form of the principle of virtual work can be written as:

$$\int_0^a \int_0^b \int_{-h/2}^{h/2} \left[\sigma_x \delta\varepsilon_x + \sigma_y \delta\varepsilon_y + \tau_{xy} \delta\gamma_{xy} + \tau_{yz} \delta\gamma_{yz} + \tau_{xz} \delta\gamma_{xz} \right] dz\,dy\,dx - \int_0^a \int_0^b q \left(\delta w_b + \delta w_s \right) dy\,dx$$

$$+ \rho \int_0^a \int_0^b \int_{-h/2}^{h/2} \left[\frac{\partial^2 u}{\partial t^2} \delta u + \frac{\partial^2 v}{\partial t^2} \delta v + \frac{\partial^2 \left(w_b + w_s \right)}{\partial t^2} \left(\delta w_b + \delta w_s \right) \right] dz\,dy\,dx \qquad (8)$$

$$- \int_0^a \int_0^b \left[N_{xx}^0 \frac{\partial^2 \left(w_b + w_s \right)}{\partial x^2} + N_{yy}^0 \frac{\partial^2 \left(w_b + w_s \right)}{\partial y^2} + 2N_{xy}^0 \frac{\partial^2 \left(w_b + w_s \right)}{\partial x \partial y} \right] \left(\delta w_b + \delta w_s \right) dy\,dx = 0$$

where δ be the variational operator. Integrating Eq. (8) by parts and collecting the coefficients of δu_0, δv_0, δw_b and δw_s, the governing equations of equilibrium and boundary conditions (Euler-Lagrange equations) associated with the present theory are obtained using fundamental lemma of calculus of variation. The governing equations of plate equilibrium are as follows:

$$\delta u_0: \quad \frac{\partial N_x}{\partial x} + \frac{\partial N_{xy}}{\partial y} = I_0 \frac{\partial^2 u}{\partial t^2} \qquad (9)$$

$$\delta v_0: \quad \frac{\partial N_y}{\partial y} + \frac{\partial N_{xy}}{\partial x} = I_0 \frac{\partial^2 v}{\partial t^2} \qquad (10)$$

$$\delta w_b: \quad \frac{\partial^2 M_x^b}{\partial x^2} + 2\frac{\partial^2 M_{xy}^b}{\partial x \partial y} + \frac{\partial^2 M_y^b}{\partial y^2} + N_{xx}^0 \frac{\partial^2 \left(w_b + w_s \right)}{\partial x^2} + N_{yy}^0 \frac{\partial^2 \left(w_b + w_s \right)}{\partial y^2}$$

$$+ 2N_{xy}^0 \frac{\partial^2 \left(w_b + w_s \right)}{\partial x \partial y} + q = I_0 \left(\frac{\partial^2 w_b}{\partial t^2} + \frac{\partial^2 w_s}{\partial t^2} \right) \qquad (11)$$

$$- I_2 \left(\frac{\partial^4 w_b}{\partial x^2 \partial t^2} + \frac{\partial^4 w_b}{\partial y^2 \partial t^2} \right) - I_3 \left(\frac{\partial^4 w_s}{\partial x^2 \partial t^2} + \frac{\partial^4 w_s}{\partial y^2 \partial t^2} \right)$$

$$\delta w_s: \quad \frac{\partial^2 M_x^s}{\partial x^2} + 2\frac{\partial^2 M_{xy}^s}{\partial x \partial y} + \frac{\partial^2 M_y^s}{\partial y^2} + \frac{\partial Q_{xz}^s}{\partial x} + \frac{\partial Q_{yz}^s}{\partial y} + N_{xx}^0 \frac{\partial^2 \left(w_b + w_s \right)}{\partial x^2}$$

$$+ N_{yy}^0 \frac{\partial^2 \left(w_b + w_s \right)}{\partial y^2} + 2N_{xy}^0 \frac{\partial^2 \left(w_b + w_s \right)}{\partial x \partial y} + q = I_0 \left(\frac{\partial^2 w_b}{\partial t^2} + \frac{\partial^2 w_s}{\partial t^2} \right) \qquad (12)$$

$$- I_3 \left(\frac{\partial^4 w_b}{\partial x^2 \partial t^2} + \frac{\partial^4 w_b}{\partial y^2 \partial t^2} \right) - I_4 \left(\frac{\partial^4 w_s}{\partial x^2 \partial t^2} + \frac{\partial^4 w_s}{\partial y^2 \partial t^2} \right)$$

Substituting the stress resultants in terms of displacement variables from Eq. (7) into the Eqs. (9) – (12), the governing equations of equilibrium can be rewritten as:

$$\delta u_0: \quad -A_{11}\frac{\partial^2 u_0}{\partial x^2} - A_{66}\frac{\partial^2 u_0}{\partial y^2} - (A_{12}+A_{66})\frac{\partial^2 v_0}{\partial x\partial y} + B_{11}\frac{\partial^3 w_b}{\partial x^3} + (B_{12}+2B_{66})\frac{\partial^3 w_b}{\partial x\partial y^2}$$

$$+As_{11}\frac{\partial^3 w_s}{\partial x^3} + (As_{12}+2As_{66})\frac{\partial^3 w_s}{\partial x\partial y^2} + I_0\frac{\partial^2 u_0}{\partial t^2} = 0 \tag{13}$$

$$\delta v_0: \quad -(A_{12}+A_{66})\frac{\partial^2 u_0}{\partial x\partial y} - A_{22}\frac{\partial^2 v_0}{\partial y^2} - A_{66}\frac{\partial^2 v_0}{\partial x^2} + B_{22}\frac{\partial^3 w_b}{\partial y^3} + (B_{12}+2B_{66})\frac{\partial^3 w_b}{\partial x^2\partial y}$$

$$+As_{22}\frac{\partial^3 w_s}{\partial y^3} + (As_{12}+2As_{66})\frac{\partial^3 w_s}{\partial x^2\partial y} + I_0\frac{\partial^2 v_0}{\partial t^2} = 0 \tag{14}$$

$$\delta w_b: \quad -B_{11}\frac{\partial^3 u_0}{\partial x^3} - (B_{12}+2B_{66})\frac{\partial^3 u_0}{\partial x\partial y^2} - B_{22}\frac{\partial^3 v_0}{\partial y^3} - (B_{12}+2B_{66})\frac{\partial^3 v_0}{\partial x^2\partial y} + D_{11}\frac{\partial^4 w_b}{\partial x^4}$$

$$+2(D_{12}+2D_{66})\frac{\partial^4 w_b}{\partial x^2\partial y^2} + D_{22}\frac{\partial^4 w_b}{\partial y^4} + Bs_{11}\frac{\partial^4 w_s}{\partial x^4} + 2(Bs_{12}+2Bs_{66})\frac{\partial^4 w_s}{\partial x^2\partial y^2}$$

$$+Bs_{22}\frac{\partial^4 w_s}{\partial y^4} + I_0\left(\frac{\partial^2 w_b}{\partial t^2} + \frac{\partial^2 w_s}{\partial t^2}\right) - I_1\left(\frac{\partial^4 w_b}{\partial x^2\partial t^2} + \frac{\partial^4 w_b}{\partial y^2\partial t^2}\right) - I_2\left(\frac{\partial^4 w_s}{\partial x^2\partial t^2} + \frac{\partial^4 w_s}{\partial y^2\partial t^2}\right) \tag{15}$$

$$= q + N_{xx}^0\frac{\partial^2(w_b+w_s)}{\partial x^2} + N_{yy}^0\frac{\partial^2(w_b+w_s)}{\partial y^2} + 2N_{xy}^0\frac{\partial^2(w_b+w_s)}{\partial x\partial y}$$

$$\delta w_s: \quad -As_{11}\frac{\partial^3 u_0}{\partial x^3} - (As_{12}+2As_{66})\frac{\partial^3 u_0}{\partial x\partial y^2} - As_{22}\frac{\partial^3 v_0}{\partial y^3} - (As_{12}+2As_{66})\frac{\partial^3 v_0}{\partial x^2\partial y} + Bs_{11}\frac{\partial^4 w_b}{\partial x^4}$$

$$+2(Bs_{12}+2Bs_{66})\frac{\partial^4 w_b}{\partial x^2\partial y^2} + Bs_{22}\frac{\partial^4 w_b}{\partial y^4} + Ass_{11}\frac{\partial^4 w_s}{\partial x^4} + 2(Ass_{12}+2Ass_{66})\frac{\partial^4 w_s}{\partial x^2\partial y^2}$$

$$+Ass_{22}\frac{\partial^4 w_s}{\partial y^4} + I_0\left(\frac{\partial^2 w_b}{\partial t^2} + \frac{\partial^2 w_s}{\partial t^2}\right) - I_2\left(\frac{\partial^4 w_b}{\partial x^2\partial t^2} + \frac{\partial^4 w_b}{\partial y^2\partial t^2}\right) - I_3\left(\frac{\partial^4 w_s}{\partial x^2\partial t^2} + \frac{\partial^4 w_s}{\partial y^2\partial t^2}\right) \tag{16}$$

$$= q + N_{xx}^0\frac{\partial^2(w_b+w_s)}{\partial x^2} + N_{yy}^0\frac{\partial^2(w_b+w_s)}{\partial y^2} + 2N_{xy}^0\frac{\partial^2(w_b+w_s)}{\partial x\partial y}$$

where $A_{ij}, B_{ij}, As_{ij}, D_{ij}, Bs_{ij}, Ass_{ij}, Acc_{ij}$ are the laminate stiffness coefficients and I_0, I_1, I_2, I_3 are the inertia constants which are given as:

$$\{A_{ij}, B_{ij}, As_{ij}, D_{ij}\} = \sum_{k=1}^{N} \bar{Q}_{ij}^k \int_{-h/2}^{h_k} \{1, z, f(z), z^2\} dz; \qquad (i=j=1,2,6)$$

$$\{Bs_{ij}, Ass_{ij}\} = \sum_{k=1}^{N} \bar{Q}_{ij}^k \int_{-h/2}^{h_k} f(z)\{z, f(z)\} dz; \qquad (i=j=1,2,6) \tag{17}$$

$$\{Acc_{ij}\} = \sum_{k=1}^{N} \bar{Q}_{ij}^{k} \int_{-h/2}^{h_k} \left[g(z) \right]^2 dz \qquad\qquad (i = j = 4,5)$$

$$(I_0, I_1) = \rho \int_{-h/2}^{h/2} (1, z^2) dz, I_2 = \rho \int_{-h/2}^{h/2} z f(z) dz, I_3 = \rho \int_{-h/2}^{h/2} \left[f(z) \right]^2 dz$$

Where

$$f(z) = z - \frac{h}{\pi} \sin \frac{\pi z}{h} \quad \text{and} \quad g(z) = \cos \frac{\pi z}{h} \tag{18}$$

This completes the mathematical formulation of the present trigonometric shear deformation theory.

4 NAVIER SOLUTION TECHNIQUE

The Navier solution technique (Szilard, 2004) is used for the bending, buckling and free vibration analysis of laminated composite plates simply supported at all four edges (pinned edges) satisfying the following boundary conditions:

$$\text{at } x = 0 \text{ and } x = a\colon v_0 = w_b = w_s = M_x^{\ b} = M_x^{\ s} = 0 \tag{19}$$

$$\text{at } y = 0 \text{ and } y = b\colon u_0 = w_b = w_s = M_y^{\ b} = M_y^{\ s} = 0 \tag{20}$$

4.1 Bending Analysis of Laminated Composite Plates

Following the Navier solution technique, the governing equations of the simply supported laminated composite plates in case of bending analysis are obtained by discarding in-plane compressive loads ($N_{xx}^0, N_{yy}^0, N_{xy}^0$) and inertia terms (I_0, I_1, I_2, I_3) from Eqs. (13) – (16).

$$-A_{11} \frac{\partial^2 u_0}{\partial x^2} - A_{66} \frac{\partial^2 u_0}{\partial y^2} - (A_{12} + A_{66}) \frac{\partial^2 v_0}{\partial x \partial y} + B_{11} \frac{\partial^3 w_b}{\partial x^3} + (B_{12} + 2B_{66}) \frac{\partial^3 w_b}{\partial x \partial y^2}$$
$$+ As_{11} \frac{\partial^3 w_s}{\partial x^3} + (As_{12} + 2As_{66}) \frac{\partial^3 w_s}{\partial x \partial y^2} = 0 \tag{21}$$

$$-(A_{12} + A_{66}) \frac{\partial^2 u_0}{\partial x \partial y} - A_{22} \frac{\partial^2 v_0}{\partial y^2} - A_{66} \frac{\partial^2 v_0}{\partial x^2} + B_{22} \frac{\partial^3 w_b}{\partial y^3} + (B_{12} + 2B_{66}) \frac{\partial^3 w_b}{\partial x^2 \partial y}$$
$$+ As_{22} \frac{\partial^3 w_s}{\partial y^3} + (As_{12} + 2As_{66}) \frac{\partial^3 w_s}{\partial x^2 \partial y} = 0 \tag{22}$$

$$-B_{11}\frac{\partial^3 u_0}{\partial x^3} - \left(B_{12} + 2B_{66}\right)\frac{\partial^3 u_0}{\partial x \partial y^2} - B_{22}\frac{\partial^3 v_0}{\partial y^3} - \left(B_{12} + 2B_{66}\right)\frac{\partial^3 v_0}{\partial x^2 \partial y} + D_{11}\frac{\partial^4 w_b}{\partial x^4} + D_{22}\frac{\partial^4 w_b}{\partial y^4}$$

$$+2\left(D_{12} + 2D_{66}\right)\frac{\partial^4 w_b}{\partial x^2 \partial y^2} + Bs_{11}\frac{\partial^4 w_s}{\partial x^4} + 2\left(Bs_{12} + 2Bs_{66}\right)\frac{\partial^4 w_s}{\partial x^2 \partial y^2} + Bs_{22}\frac{\partial^4 w_s}{\partial y^4} = q \tag{23}$$

$$-As_{11}\frac{\partial^3 u_0}{\partial x^3} - \left(As_{12} + 2As_{66}\right)\frac{\partial^3 u_0}{\partial x \partial y^2} - As_{22}\frac{\partial^3 v_0}{\partial y^3} - \left(As_{12} + 2As_{66}\right)\frac{\partial^3 v_0}{\partial x^2 \partial y} + Bs_{11}\frac{\partial^4 w_b}{\partial x^4} + Bs_{22}\frac{\partial^4 w_b}{\partial y^4}$$

$$+2\left(Bs_{12} + 2Bs_{66}\right)\frac{\partial^4 w_b}{\partial x^2 \partial y^2} + Ass_{11}\frac{\partial^4 w_s}{\partial x^4} + 2\left(Ass_{12} + 2Ass_{66}\right)\frac{\partial^4 w_s}{\partial x^2 \partial y^2} + Ass_{22}\frac{\partial^4 w_s}{\partial y^4} = q \tag{24}$$

The plate is subjected to transverse load $q(x, y)$ at top surface *i.e.* $z = -h/2$. The transverse load is presented in double trigonometric series as given in Eq. (25).

$$q(x, y) = \sum_{m=1,3,5}^{\infty} \sum_{n=1,3,5}^{\infty} q_{mn} \sin\alpha x \sin\beta y \tag{25}$$

where $\alpha = m\pi/a$, $\beta = n\pi/b$ and q_{mn} is the coefficient of Fourier expansion. The coefficient of Fourier expansion $\left(q_{mn}\right)$ is:

$$q_{mn} = q_0 \qquad \text{Sinusoidally distributed Load } (m = 1, n = 1) \tag{26}$$

where q_0 is the maximum intensity of load at the center of plate. The following solution form is assumed for the unknown displacement variables u_0, v_0, w_b and w_s satisfying the boundary conditions of simply supported plates exactly.

$$\begin{Bmatrix} u_0 \\ v_0 \\ w_b \\ w_s \end{Bmatrix} = \sum_{m=1,3,5}^{\infty} \sum_{n=1,3,5}^{\infty} \begin{Bmatrix} u_{mn}\cos\alpha x \sin\beta y \\ v_{mn}\sin\alpha x \cos\beta y \\ w_{bmn}\sin\alpha x \sin\beta y \\ w_{smn}\sin\alpha x \sin\beta y \end{Bmatrix} \tag{27}$$

where u_{mn}, v_{mn}, w_{bmn} and w_{smn} are the unknown constants to be determined. In case of sinusoidally distributed load, positive integers are unity ($m = 1$, $n = 1$). Substitution of this form of solution and transverse load $q(x, y)$ into the governing equations (21) - (24) leads to the set of algebraic equations which can be written in matrix form as follows.

$$\begin{bmatrix} K_{11} & K_{12} & K_{13} & K_{14} \\ K_{12} & K_{22} & K_{23} & K_{24} \\ K_{13} & K_{23} & K_{33} & K_{34} \\ K_{14} & K_{24} & K_{34} & K_{44} \end{bmatrix} \begin{Bmatrix} u_{mn} \\ v_{mn} \\ w_{bmn} \\ w_{smn} \end{Bmatrix} = \begin{Bmatrix} 0 \\ 0 \\ q_0 \\ q_0 \end{Bmatrix} \tag{28}$$

where elements of stiffness matrix $[K]$ are as follows:

$$K_{11} = A_{11}\alpha^2 + A_{66}\beta^2, \quad K_{12} = (A_{12} + A_{66})\alpha\beta, \quad K_{13} = -\left[\alpha^3 B_{11} + (B_{12} + 2B_{66})\alpha\beta^2\right],$$

$$K_{14} = -\left[\alpha^3 As_{11} + (As_{12} + 2As_{66})\alpha\beta^2\right], \quad K_{22} = A_{22}\beta^2 + A_{66}\alpha^2,$$

$$K_{23} = -\left[\beta^3 B_{22} + (B_{12} + 2B_{66})\alpha^2\beta\right], \quad K_{24} = -\left[\beta^3 As_{22} + (As_{12} + 2As_{66})\alpha^2\beta\right],$$

$$K_{33} = D_{11}\alpha^4 + 2(D_{12} + 2D_{66})\alpha^2\beta^2 + D_{22}\beta^4, \quad K_{34} = Bs_{11}\alpha^4 + 2(Bs_{12} + 2Bs_{66})\alpha^2\beta^2 + Bs_{22}\beta^4, \quad (29)$$

$$K_{44} = Ass_{11}\alpha^4 + 2(Ass_{12} + 2Ass_{66})\alpha^2\beta^2 + Ass_{22}\beta^4 + Acc_{55}\alpha^2 + Acc_{44}\beta^2,$$

$$K_{21} = K_{12}, K_{31} = K_{13}, K_{32} = K_{23}, K_{41} = K_{14}, K_{42} = K_{24}, K_{43} = K_{34}.$$

From the solution of Eq. (28), unknown constants u_{mn}, v_{mn}, w_{bmn} and w_{smn} can be obtained. Having obtained values of these unknown constants one can then calculate all the displacement and stress components within the plate using Eqs. (3) - (5). Transverse shear stresses (τ_{xz}, τ_{yz}) are obtained by using constitutive relations $(\tau_{xz}^{CR}, \tau_{yz}^{CR})$ and integrating equations of equilibrium of theory of elasticity $(\tau_{xz}^{EE}, \tau_{yz}^{EE})$ to ascertain the continuity at layer interface. The following material properties are used for the bending analysis of simply supported anti-symmetric laminated composite square plates subjected to sinusoidally distributed load.

$$E_1 = 25E_2, \quad G_{12} = G_{13} = 0.5E_2, \quad G_{23} = 0.2E_2, \quad \mu_{12} = 0.25, \quad \mu_{21} = \frac{E_2}{E_1}\mu_{12} \quad (30)$$

The displacements and stresses are presented in the following non-dimensional form.

$$\bar{u}\left(0, \frac{b}{2}, -\frac{h}{2}\right) = \frac{u E_2 h^2}{q_0 a^3}, \quad \bar{w}\left(\frac{a}{2}, \frac{b}{2}, 0\right) = \frac{100 w h^3 E_2}{q_0 a^4},$$

$$\bar{\sigma}_x\left(\frac{a}{2}, \frac{b}{2}, -\frac{h}{2}\right) = \frac{\sigma_x h^2}{q_0 a^2}, \quad \bar{\sigma}_y\left(\frac{a}{2}, \frac{b}{2}, -\frac{h}{2}\right) = \frac{\sigma_y h^2}{q_0 a^2}, \quad (31)$$

$$\bar{\tau}_{xy}\left(0, 0, -\frac{h}{2}\right) = \frac{\tau_{xy} h^2}{q_0 a^2}, \quad \bar{\tau}_{xz}\left(0, \frac{b}{2}, 0\right) = \frac{\tau_{xz} h}{q_0 a}, \quad \bar{\tau}_{yz}\left(\frac{a}{2}, 0, 0\right) = \frac{\tau_{yz} h}{q_0 a}$$

a/h	Quantity	Exact (Pagano, 1970)	Present	SSNDT (Sayyad and Ghugal, 2014a)	HSDT (Reddy,1984)	FSDT (Mindlin,1951)	CPT (Kirchhoff,1850)
4	$\bar{u}$	---	0.0114	0.0111	0.0114	0.0088	0.0088
	$\bar{w}$	2.0670	1.9793	1.9424	2.0256	1.9682	1.0636
	$\bar{\sigma}_x$	0.8410	0.9154	0.9062	0.9172	0.7157	0.7157
	$\bar{\sigma}_y$	0.1090	0.0890	0.0964	0.0932	0.0843	0.0843
	$\bar{\tau}_{xy}$	0.0591	0.0578	0.0562	0.0713	0.0525	0.0525
	$\bar{\tau}_{xz}^{CR}$	0.1200	0.0660	0.1270	0.1270	0.0910	---
	$\bar{\tau}_{xz}^{EE}$	0.1200	0.1091	0.1120	0.1100	0.1220	0.1220
	$\bar{\tau}_{yz}^{CR}$	0.1350	0.1276	0.1270	0.1270	0.0910	---
	$\bar{\tau}_{yz}^{EE}$	0.1350	0.1091	0.1120	0.1103	0.1220	0.1220
10	$\bar{u}$	---	0.0093	0.0092	0.0095	0.0088	0.0088
	$\bar{w}$	1.2250	1.2135	1.2089	1.2479	1.2083	1.0636
	$\bar{\sigma}_x$	0.7302	0.7484	0.7471	0.7652	0.7157	0.7157
	$\bar{\sigma}_y$	0.0886	0.0851	0.0876	0.0889	0.0843	0.0843
	$\bar{\tau}_{xy}$	0.0535	0.0534	0.0530	0.0680	0.0525	0.0525
	$\bar{\tau}_{xz}^{CR}$	0.1210	0.1270	0.1300	0.1310	0.0910	---
	$\bar{\tau}_{xz}^{EE}$	0.1210	0.1199	0.1200	0.1200	0.1220	0.1220
	$\bar{\tau}_{yz}^{CR}$	0.1250	0.1306	0.1300	0.1310	0.0910	---
	$\bar{\tau}_{yz}^{EE}$	0.1250	0.1199	0.1200	0.1200	0.1220	0.1220

Table 1: Comparison of non-dimensional displacements and stresses for the two layered $(0^0/90^0)$ laminated composite square $(b = a)$ plate subjected to sinusoidally distributed load.
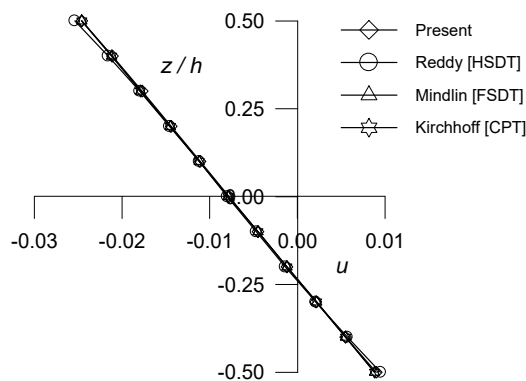

Figure 2: Through thickness distribution of in-plane displacement $(\bar{u})$ for two layered $(0^0/90^0)$ laminated composite plate subjected to sinusoidally distributed load $(b = a, a/h = 10)$.
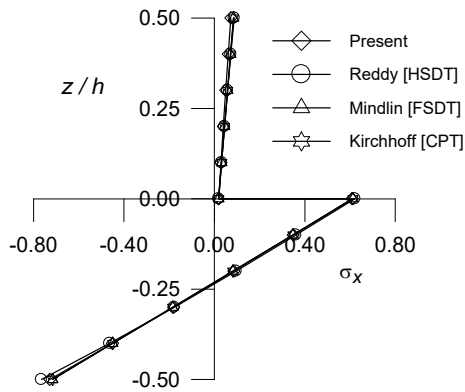
Figure 3: Through thickness distribution of in-plane normal stress ($\overline{\sigma}_x$) for two layered ($0^0/90^0$) laminated composite plate subjected to sinusoidally distributed load ($b = a$, $a/h = 10$).

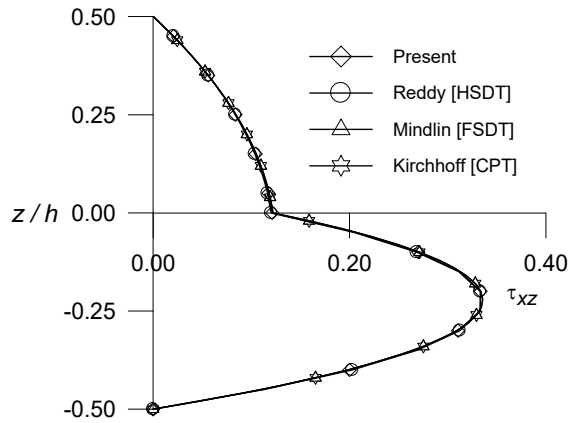**Figure 4**: Through thickness distribution of transverse shear stress (τ_{xz}^{EE}) for two layered ($0^0/90^0$) laminated composite plate subjected to sinusoidally distributed load ($b = a$, $a/h = 10$).

4.2 Buckling Analysis of Laminated Composite Plates

In this section, an analytical solution for the buckling analysis of plate is developed using Navier solution technique. The governing equations of the plate in case of static buckling are obtained by discarding transverse load (q) and inertia terms (I_0, I_1, I_2, I_3) from Eqs. (13) – (16). The in-plane compressive (N_{xx}^0, N_{yy}^0 and N_{xy}^0) forces now represents loads instead of reaction forces, as there is no transverse load. The values of in-plane compressive forces are taken as $N_{xx}^0 = -k_1 N_0$, $N_{yy}^0 = -k_2 N_0$ and $N_{xy}^0 = 0$. The governing equations for static buckling are as follows:

$$-A_{11} \frac{\partial^2 u_0}{\partial x^2} - A_{66} \frac{\partial^2 u_0}{\partial y^2} - \left(A_{12} + A_{66}\right)\frac{\partial^2 v_0}{\partial x \partial y} + B_{11} \frac{\partial^3 w_b}{\partial x^3} + \left(B_{12} + 2B_{66}\right)\frac{\partial^3 w_b}{\partial x \partial y^2}$$
$$+ As_{11} \frac{\partial^3 w_s}{\partial x^3} + \left(As_{12} + 2As_{66}\right)\frac{\partial^3 w_s}{\partial x \partial y^2} = 0 \tag{32}$$

$$-\left(A_{12}+A_{66}\right)\frac{\partial^2 u_0}{\partial x \partial y}-A_{22}\frac{\partial^2 v_0}{\partial y^2}-A_{66}\frac{\partial^2 v_0}{\partial x^2}+B_{22}\frac{\partial^3 w_b}{\partial y^3}+\left(B_{12}+2B_{66}\right)\frac{\partial^3 w_b}{\partial x^2 \partial y}$$

$$+As_{22}\frac{\partial^3 w_s}{\partial y^3}+\left(As_{12}+2As_{66}\right)\frac{\partial^3 w_s}{\partial x^2 \partial y}=0 \tag{33}$$

$$-B_{11}\frac{\partial^3 u_0}{\partial x^3}-\left(B_{12}+2B_{66}\right)\frac{\partial^3 u_0}{\partial x \partial y^2}-B_{22}\frac{\partial^3 v_0}{\partial y^3}-\left(B_{12}+2B_{66}\right)\frac{\partial^3 v_0}{\partial x^2 \partial y}+D_{11}\frac{\partial^4 w_b}{\partial x^4}$$

$$+2\left(D_{12}+2D_{66}\right)\frac{\partial^4 w_b}{\partial x^2 \partial y^2}+D_{22}\frac{\partial^4 w_b}{\partial y^4}+Bs_{11}\frac{\partial^4 w_s}{\partial x^4}+2\left(Bs_{12}+2Bs_{66}\right)\frac{\partial^4 w_s}{\partial x^2 \partial y^2} \tag{34}$$

$$+Bs_{22}\frac{\partial^4 w_s}{\partial y^4}+N_0\left(k_1\frac{\partial^2\left(w_b+w_s\right)}{\partial x^2}+k_2\frac{\partial^2\left(w_b+w_s\right)}{\partial y^2}\right)=0$$

$$-As_{11}\frac{\partial^3 u_0}{\partial x^3}-\left(As_{12}+2As_{66}\right)\frac{\partial^3 u_0}{\partial x \partial y^2}-As_{22}\frac{\partial^3 v_0}{\partial y^3}-\left(As_{12}+2As_{66}\right)\frac{\partial^3 v_0}{\partial x^2 \partial y}+Bs_{11}\frac{\partial^4 w_b}{\partial x^4}$$

$$+2\left(Bs_{12}+2Bs_{66}\right)\frac{\partial^4 w_b}{\partial x^2 \partial y^2}+Bs_{22}\frac{\partial^4 w_b}{\partial y^4}+Ass_{11}\frac{\partial^4 w_s}{\partial x^4}+2\left(Ass_{12}+2Ass_{66}\right)\frac{\partial^4 w_s}{\partial x^2 \partial y^2} \tag{35}$$

$$+Ass_{22}\frac{\partial^4 w_s}{\partial y^4}+N_0\left(k_1\frac{\partial^2\left(w_b+w_s\right)}{\partial x^2}+k_2\frac{\partial^2\left(w_b+w_s\right)}{\partial y^2}\right)=0$$

where N_0 is the intensity of in-plane compressive force. After substituting Eq. (27) into Eqs. (32) – (35), the following system of equations in matrix form is obtained.

$$\left\{\begin{bmatrix} K_{11} & K_{12} & K_{13} & K_{14} \\ K_{12} & K_{22} & K_{23} & K_{24} \\ K_{13} & K_{23} & K_{33} & K_{34} \\ K_{14} & K_{24} & K_{34} & K_{44} \end{bmatrix}-N_0\begin{bmatrix} 0 & 0 & 0 & 0 \\ 0 & 0 & 0 & 0 \\ 0 & 0 & k_1\alpha^2+k_2\beta^2 & k_1\alpha^2+k_2\beta^2 \\ 0 & 0 & k_1\alpha^2+k_2\beta^2 & k_1\alpha^2+k_2\beta^2 \end{bmatrix}\right\}\begin{Bmatrix} u_{mn} \\ v_{mn} \\ w_{bmn} \\ w_{smn} \end{Bmatrix}=\begin{Bmatrix} 0 \\ 0 \\ 0 \\ 0 \end{Bmatrix} \tag{36}$$

where the element of stiffness matrix $[K_{ij}]$ are given in Eq. (29). For nontrivial solution, the determinant of the coefficient matrix in Eq. (36) must be zero. For each choice of m and n, there is a corresponding unique value of N_0. The critical buckling load is the smallest value of $N_0(m, n)$. A simply supported laminated composite square and rectangular plates subjected to the uniaxial and biaxial loading conditions, as shown in Figure 5, is considered to illustrate the accuracy of the present theory in predicting the buckling behaviour. The following material properties are used in the numerical study.

$$E_1/E_2=\text{open}, \ \ G_{12}=G_{13}=0.6E_2, \ \ G_{23}=0.5E_2, \ \ \mu_{12}=0.25, \ \ \mu_{21}=\frac{E_2}{E_1}\mu_{12} \tag{37}$$

Critical buckling loads are presented in the following non-dimensional form:

$$N_{cr} = \left(N_0\, a^2\right)/\left(E_2\, h^3\right) \tag{38}$$

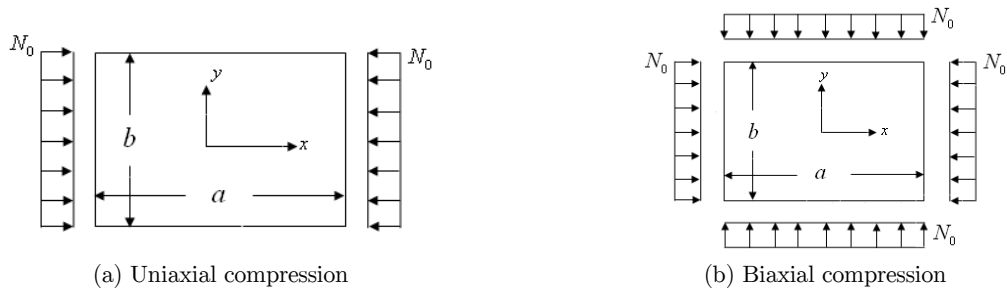(a) Uniaxial compression   (b) Biaxial compression

Figure 5: A simply supported plate subjected to in-plane compressive forces.

Layup	Compression	(k_1, k_2)	Source	E_1 / E_2		
				20	30	40
$(0^0/90^0/0^0)$	Uniaxial	(1, 0)	Present	15.215	20.428	24.977
			SSNDT (Sayyad and Ghugal, 2014b)	15.003	19.002	22.330
			HSDT (Reddy, 1984)	15.300	19.675	23.339
			FSDT (Mindlin, 1951)	14.985	19.027	22.315
			CPT (Kirchhoff, 1850)	19.712	27.936	36.160
			Exact (Noor, 1975)	15.019	19.304	22.880
	Biaxial	(1, 1)	Present	7.6075	10.214	12.488
			SSNDT (Sayyad and Ghugal, 2014b)	7.5014	9.5009	11.165
			HSDT (Reddy, 1984)	7.6500	9.8376	11.669
			FSDT (Mindlin, 1951)	7.4925	9.5135	11.157
			CPT (Kirchhoff, 1850)	9.8560	13.968	18.080
			Exact (Noor, 1975)	7.5095	9.6520	11.440
$(0^0/90^0/0^0/90^0/0^0)$	Uniaxial	(1, 0)	Present	16.234	21.435	25.976
			SSNDT (Sayyad and Ghugal, 2014b)	15.828	20.643	24.756
			HSDT (Reddy, 1984)	15.783	20.578	24.676
			FSDT (Mindlin, 1951)	15.736	20.485	24.547
			CPT (Kirchhoff, 1850)	19.712	27.936	36.160
			Exact (Noor, 1975)	15.653	20.466	24.593
	Biaxial	(1, 1)	Present	8.117	10.717	12.988
			SSNDT (Sayyad and Ghugal, 2014b)	7.9140	10.321	12.378
			HSDT (Reddy, 1984)	7.8915	10.289	12.338
			FSDT (Mindlin, 1951)	7.8680	10.240	12.273
			CPT (Kirchhoff, 1850)	9.8560	13.968	18.080
			Exact (Noor, 1975)	7.8265	10.466	12.296

Table 2: Comparison of critical buckling load (N_{cr}) for simply supported laminated composite square plates under uniaxial and biaxial compression ($b = a$, $a/h = 10$).

Compression	(k_1, k_2)	a/h	Source	b/a			
				1.0	2.0	3.0	4.0
Uniaxial	(1, 0)	5	Present	14.181	9.950	9.091	8.778
			SSNDT (Sayyad and Ghugal, 2014b)	11.986	8.780	8.463	8.382
			FSDT (Mindlin, 1951)	12.146	8.673	8.357	8.279
			CPT (Kirchhoff, 1850)	36.160	29.833	29.259	29.102
		10	Present	25.908	19.785	18.705	18.313
			SSNDT (Sayyad and Ghugal, 2014b)	23.387	18.500	18.057	17.941
			FSDT (Mindlin, 1951)	23.453	18.398	17.962	17.849
			CPT (Kirchhoff, 1850)	36.160	29.833	29.259	29.102
		100	Present	36.016	29.682	29.094	28.931
			SSNDT (Sayyad and Ghugal, 2014b)	35.961	29.652	29.080	28.924
			FSDT (Mindlin, 1951)	35.956	29.648	29.077	28.921
			CPT (Kirchhoff, 1850)	36.160	29.833	29.259	29.102
Biaxial	(1, 1)	5	Present	7.0900	7.9600	8.1820	8.2620
			SSNDT (Sayyad and Ghugal, 2014b)	5.9934	7.0244	7.6171	7.8896
			FSDT (Mindlin, 1951)	6.0730	6.9387	7.5216	7.7928
			CPT (Kirchhoff, 1850)	18.080	23.866	26.333	27.390
		10	Present	12.954	15.828	16.834	17.236
			SSNDT (Sayyad and Ghugal, 2014b)	11.694	14.800	16.251	16.886
			FSDT (Mindlin, 1951)	11.726	14.719	16.166	16.799
			CPT (Kirchhoff, 1850)	18.080	23.866	26.333	27.390
		100	Present	18.008	23.746	26.185	27.229
			SSNDT (Sayyad and Ghugal, 2014b)	17.980	23.722	26.172	27.223
			FSDT (Mindlin, 1951)	17.978	23.718	26.169	27.219
			CPT (Kirchhoff, 1850)	18.080	23.866	26.333	27.390

Table 3: Comparison of critical buckling load (N_{cr}) for simply supported four layered ($0^0/90^0/90^0/0^0$) laminated composite rectangular plates under uniaxial and biaxial compression.

4.3 Free Vibration Analysis of Laminated Composite Plates

According to Navier solution technique, the governing equations of the plate in case of free vibration analysis are obtained by discarding transverse load (q) and in-plane compressive forces ($N_{xx}^0, N_{yy}^0, N_{xy}^0$) from Eq. (13) – (16). These equations are as follows:

$$-A_{11}\frac{\partial^2 u_0}{\partial x^2} - A_{66}\frac{\partial^2 u_0}{\partial y^2} - (A_{12} + A_{66})\frac{\partial^2 v_0}{\partial x \partial y} + B_{11}\frac{\partial^3 w_b}{\partial x^3} + (B_{12} + 2B_{66})\frac{\partial^3 w_b}{\partial x \partial y^2}$$
$$+As_{11}\frac{\partial^3 w_s}{\partial x^3} + (As_{12} + 2As_{66})\frac{\partial^3 w_s}{\partial x \partial y^2} + I_0\frac{\partial^2 u_0}{\partial t^2} = 0 \tag{39}$$

$$-\left(A_{12}+A_{66}\right)\frac{\partial^2 u_0}{\partial x \partial y}-A_{22}\frac{\partial^2 v_0}{\partial y^2}-A_{66}\frac{\partial^2 v_0}{\partial x^2}+B_{22}\frac{\partial^3 w_b}{\partial y^3}+\left(B_{12}+2B_{66}\right)\frac{\partial^3 w_b}{\partial x^2 \partial y}$$

$$+As_{22}\frac{\partial^3 w_s}{\partial y^3}+\left(As_{12}+2As_{66}\right)\frac{\partial^3 w_s}{\partial x^2 \partial y}+I_0\frac{\partial^2 v_0}{\partial t^2}=0 \tag{40}$$

$$-B_{11}\frac{\partial^3 u_0}{\partial x^3}-\left(B_{12}+2B_{66}\right)\frac{\partial^3 u_0}{\partial x \partial y^2}-B_{22}\frac{\partial^3 v_0}{\partial y^3}-\left(B_{12}+2B_{66}\right)\frac{\partial^3 v_0}{\partial x^2 \partial y}+D_{11}\frac{\partial^4 w_b}{\partial x^4}$$

$$+2\left(D_{12}+2D_{66}\right)\frac{\partial^4 w_b}{\partial x^2 \partial y^2}+D_{22}\frac{\partial^4 w_b}{\partial y^4}+Bs_{11}\frac{\partial^4 w_s}{\partial x^4}+2\left(Bs_{12}+2Bs_{66}\right)\frac{\partial^4 w_s}{\partial x^2 \partial y^2} \tag{41}$$

$$+Bs_{22}\frac{\partial^4 w_s}{\partial y^4}+I_0\left(\frac{\partial^2 w_b}{\partial t^2}+\frac{\partial^2 w_s}{\partial t^2}\right)-I_1\left(\frac{\partial^4 w_b}{\partial x^2 \partial t^2}+\frac{\partial^4 w_b}{\partial y^2 \partial t^2}\right)-I_2\left(\frac{\partial^4 w_s}{\partial x^2 \partial t^2}+\frac{\partial^4 w_s}{\partial y^2 \partial t^2}\right)=0$$

$$-As_{11}\frac{\partial^3 u_0}{\partial x^3}-\left(As_{12}+2As_{66}\right)\frac{\partial^3 u_0}{\partial x \partial y^2}-As_{22}\frac{\partial^3 v_0}{\partial y^3}-\left(As_{12}+2As_{66}\right)\frac{\partial^3 v_0}{\partial x^2 \partial y}+Bs_{11}\frac{\partial^4 w_b}{\partial x^4}$$

$$+2\left(Bs_{12}+2Bs_{66}\right)\frac{\partial^4 w_b}{\partial x^2 \partial y^2}+Bs_{22}\frac{\partial^4 w_b}{\partial y^4}+Ass_{11}\frac{\partial^4 w_s}{\partial x^4}+2\left(Ass_{12}+2Ass_{66}\right)\frac{\partial^4 w_s}{\partial x^2 \partial y^2} \tag{42}$$

$$+Ass_{22}\frac{\partial^4 w_s}{\partial y^4}+I_0\left(\frac{\partial^2 w_b}{\partial t^2}+\frac{\partial^2 w_s}{\partial t^2}\right)-I_2\left(\frac{\partial^4 w_b}{\partial x^2 \partial t^2}+\frac{\partial^4 w_b}{\partial y^2 \partial t^2}\right)-I_3\left(\frac{\partial^4 w_s}{\partial x^2 \partial t^2}+\frac{\partial^4 w_s}{\partial y^2 \partial t^2}\right)=0$$

The following solution form is assumed for unknown displacement variables u_0, v_0, w_b and w_s

$$\begin{Bmatrix} u_0 \\ v_0 \\ w_b \\ w_s \end{Bmatrix} = \sum_{m=1,3,5}^{\infty}\ \sum_{n=1,3,5}^{\infty} \begin{Bmatrix} u_{mn}\cos\alpha x\,\sin\beta y\,\sin\omega t \\ v_{mn}\sin\alpha x\,\cos\beta y\,\sin\omega t \\ w_{bmn}\sin\alpha x\,\sin\beta y\,\sin\omega t \\ w_{smn}\sin\alpha x\,\sin\beta y\,\sin\omega t \end{Bmatrix} \tag{43}$$

Substituting Eq. (43) into the Eqs. (39) – (42), the following system of equations is obtained.

$$\left\{ \begin{bmatrix} K_{11} & K_{12} & K_{13} & K_{14} \\ K_{12} & K_{22} & K_{23} & K_{24} \\ K_{13} & K_{23} & K_{33} & K_{34} \\ K_{14} & K_{24} & K_{34} & K_{44} \end{bmatrix} -\omega^2 \begin{bmatrix} I_0 & 0 & 0 & 0 \\ 0 & I_0 & 0 & 0 \\ 0 & 0 & I_1(\alpha^2+\beta^2)+I_0 & I_2(\alpha^2+\beta^2)+I_0 \\ 0 & 0 & I_2(\alpha^2+\beta^2)+I_0 & I_3(\alpha^2+\beta^2)+I_0 \end{bmatrix} \right\} \begin{Bmatrix} u_{mn} \\ v_{mn} \\ w_{bmn} \\ w_{smn} \end{Bmatrix} = \begin{Bmatrix} 0 \\ 0 \\ 0 \\ 0 \end{Bmatrix} \tag{44}$$

The elements of stiffness matrix $[K]$ are given in Eq. (29). From the solution of Eq. (44) lowest natural frequencies for laminated composite plates can be obtained. The material properties given by Eq. (37) are used for the numerical study. Natural frequencies are presented in the following non-dimensional form:

$$\bar{\omega}=\omega\sqrt{\rho h^2 / E_2} \tag{45}$$

Lay-up	Source	E_1 / E_2			
		10	20	30	40
$0^0/90^0$	Present	0.27987	0.31354	0.34128	0.36498
	SSNDT (Sayyad and Ghugal, 2015)	0.28060	0.31415	0.34181	0.36543
	HSDT (Reddy, 1984)	0.27955	0.31284	0.34020	0.36348
	FSDT (Mindlin, 1951)	0.27757	0.30824	0.33284	0.35353
	CPT (Kirchhoff, 1850)	0.30968	0.35422	0.39335	0.42884
	Exact (Noor, 1973)	0.27938	0.30698	0.32705	0.34250
$0^0/90^0/0^0$	Present	0.34261	0.40623	0.44502	0.47162
	SSNDT (Sayyad and Ghugal, 2015)	0.32696	0.37037	0.39498	0.41176
	HSDT(Reddy, 1984)	0.33095	0.38112	0.41094	0.43155
	FSDT (Mindlin, 1951)	0.32739	0.37110	0.39540	0.41158
	CPT (Kirchhoff, 1850)	0.42599	0.55793	0.66419	0.75565
	Exact (Noor, 1973)	0.32841	0.38241	0.41089	0.43006
$0^0/90^0/90^0/0^0$	Present	0.3422	0.4055	0.4441	0.4706
	SSNDT (Sayyad and Ghugal, 2015)	0.3319	0.3821	0.4119	0.4324
	HSDT(Reddy, 1984)	0.3308	0.3810	0.4108	0.4314
	FSDT (Mindlin, 1951)	0.3319	0.3826	0.4130	0.4341
	CPT (Kirchhoff, 1850)	0.4260	0.5579	0.6642	0.7556
	Exact (Noor, 1973)	0.3284	0.3824	0.4108	0.4300
$0^0/90^0/0^0/90^0/0^0$	Present	0.3430	0.4063	0.4449	0.4715
	SSNDT (Sayyad and Ghugal, 2015)	0.3384	0.3950	0.4287	0.4518
	HSDT(Reddy, 1984)	0.3399	0.3994	0.4350	0.4592
	FSDT (Mindlin, 1951)	0.3368	0.3930	0.4271	0.4506
	CPT (Kirchhoff, 1850)	0.4259	0.5579	0.6641	0.7556
	Exact (Noor, 1973)	0.3408	0.3979	0.4314	0.4537

Table 4: Comparison of non-dimensional natural frequencies of simply supported square
laminated composite plates ($b = a$, $a/h = 5$).

5 DISCUSSION OF NUMERICAL RESULTS

5.1 Bending Analysis of Laminated Composite Plates

In this example the efficacy of present theory is proved for the bending analysis of simply supported
two layered ($0^0/90^0$) anti-symmetric laminated composite square plates subjected to sinusoidally dis-
tributed load. The non-dimensional displacement and stresses obtained using present theory are com-
pared and discussed with those obtained by classical plate theory (CPT) of Kirchhoff (1850), first
order shear deformation theory (FSDT) of Mindlin (1951), higher order shear deformation theory
(HSDT) of Reddy (1984), sinusoidal shear and normal deformation theory (SSNDT) of Sayyad and
Ghugal (2014a) and exact elasticity solution given by Pagano (1970). The non-dimensional numerical
results are summarized in Table 1. It is observed that the in-plane displacement predicted by present
theory is in good agreement with other theories. In-plane displacement is maximum in 90^0 layer
whereas minimum in 0^0 layer (Figure 2). The present theory underestimates the value of transverse
displacement for aspect ratio 4 but it is in good agreement with exact solution and other higher order

theories for aspect ratio 10. Figure 3 shows that, in-plane normal stress $\left(\bar{\sigma}_x\right)$ predicted by present theory is in close agreement with that of other theories. The present theory predicts exact values of transverse shear stress $\left(\bar{\tau}_{xz}\right)$ for aspect ratios 4 and 10 when obtained via equations of equilibrium $\left(\bar{\tau}_{xz}^{EE}\right)$. Through thickness distribution of this stress is shown in Figure 4.

5.2 Buckling Analysis of Laminated Composite Plates

A comparison of the critical buckling load parameters obtained by the present theory for a three layered $(0^0/90^0/0^0)$ and five layered $(0^0/90^0/0^0/90^0/0^0)$ symmetric cross-ply laminated composite square plates subjected to uniaxial and biaxial compressions for various modular ratios (E_1/E_2) is presented in Table 2. All the layers are of equal thickness. The results of present theory are compared with HSDT of Reddy (1984), SSNDT of Sayyad and Ghugal (2014b) FSDT of Mindlin (1951) and CPT of Kirchhoff (1850) and exact elasticity solution given by Noor (1975). The material properties used for this example are shown in Eq. (37). From the examination of Table 2 it is observed that the present results are in excellent agreement with exact solution as well as HSDT of Reddy (1984). It is also observed that the buckling loads predicted by CPT are significantly higher than those obtained by the present theory. This is the consequence of neglecting the transverse shear deformation effect in the CPT. It can be seen from Table 2 that the critical buckling loads in case of biaxial compression are exactly half of those of uniaxial compression for square plates. Table 3 shows the critical buckling load parameter for four layered $(0^0/90^0/90^0/0^0)$ symmetric laminated composite rectangular plate. The numerical results are obtained for various values of b/a ratios and a/h ratios. From Table 3 it is observed that the critical buckling load increases with respect to increase in 'b/a' and 'a/h' ratios. It is also pointed out that the present theory is in excellent agreement while predicting the buckling behaviour of rectangular laminated composite plates.

5.3 Free Vibration Analysis of Laminated Composite Plates

In Table 4, non-dimensional natural frequencies of simply supported square laminated composite plates for various modular ratios (E_1/E_2) are presented and compared with those obtained by SSNDT of Sayyad and Ghugal (2015), HSDT of Reddy (1984), FSDT of Mindlin (1951) and CPT of Kirchhoff (1850). In all the lamination schemes, the layers are of equal thickness. The material properties are shown in Equation (37). The exact elasticity solution for free vibration analysis of laminated composite plates given by Noor (1973) is used for the purpose of comparison. From the Table 8 it is observed that the present theory is in excellent agreement while predicting the natural frequencies of laminated composite plates. The CPT overestimates the natural frequencies because of neglect of the transverse shear deformation effect. It is also observed that the natural frequencies of laminated composite plates increase with respect to increase in modular ratios (E_1/E_2).

6 CONCLUSIONS

In the present study, a refined trigonometric shear deformation theory is applied for the bending, buckling and free vibration analysis of laminated composite plates. The most important feature of the present theory is that it involves only four unknowns which are five in case of first order shear

deformation theory and other higher order theories. The present theory satisfies the traction free conditions at top and bottom surfaces of plates without using shear correction factor. From the mathematical formulation of present theory, it is observed that, due to four unknown variables, the present theory requires less computational efforts compared to five and six variable shear deformation theories. From the numerical results and discussion it is concluded that present theory is in good agreement while predicting the bending, buckling and free vibration behaviour of laminated composite plates.

References

Ameur, M., Tounsi, A., Mechab, I. and Bedia, E.A.A., (2011). A new trigonometric shear deformation theory for bending analysis of functionally graded plate resting on elastic foundation, KSCE J. of Civil Engineering, 15:1405-1414.

Daouadji, T.H., Tounsi, A., Hadji, L., Henni, A.H. and Bedia, E.A.A., (2012). A theoretical analysis for static and dynamic behavior of functionally graded plates, Material Physics and Mechanics, 14:110-128.

Daouadji, T.H., Tounsi, A. and Bedia, E.A.A., (2013). A new higher order shear deformation model for static behavior of functionally graded plates, Advances in Applied Mathematics and Mechanics, 5:351-364.

Ghugal, Y.M. and Sayyad, A.S., (2010). A static flexure of thick isotropic plates using trigonometric shear deformation theory, J. of Solid Mechanics, 2:79–90.

Ghugal, Y.M. and Sayyad, A.S., (2013a). Static flexure of thick orthotropic plates using trigonometric shear deformation theory, J. of Structural Engineering, (India) 39:512–521.

Ghugal, Y.M. and Sayyad, A.S., (2013b). Stress analysis of thick laminated plates using trigonometric shear deformation theory, Int. J. of Applied Mechanics, 5:1–23.

Jones, R.M. 1975. Mechanics of Composite Materials, Tokyo: McGraw Hill Kogakusha Ltd.

Karama, M., Afaq, K.S. and Mistou, S., (2009). A new theory for laminated composite plates, Proc. IMechE Part L: J. Materials: Design and Applications, 223:53-62.

Kim, S.E., Thai, H.T. and Lee, J., (2009). Buckling analysis of plates using the two variable refined plate theory, Thin Walled Structure, 47:455–462.

Kirchhoff, G.R., (1850). Uber das gleichgewicht und die bewegung einer elastischen Scheibe, J. für die Reine und Angewandte Mathematik (Crelle's Journal), 40: 51-88.

Meiche, N.E., Tounsi, A., Ziane, N., Mechab, I. and Bedia, E.A.A., (2011). New hyperbolic shear deformation theory for buckling and vibration of functionally graded sandwich plate, Int. J. of Mechanical Sciences, 53:237–247.

Metin, A., (2009). A new shear deformation theory for laminated composite plates, Composite Structures, 89:94–101.

Mindlin, R.D., (1951). Influence of rotatory inertia and shear on flexural motions of isotropic, elastic plates, ASME J. of Applied Mechanics, 18: 31-38.

Noor, A.K., (1973). Free vibrations of multilayered composite plates, AIAA J. 11:1038-1039.

Noor, A.K., (1975). Stability of multilayered composite plates, Fibre Science and Technology, 8:2 81-89.

Pagano, N.J., (1970). Exact solutions for bidirectional composites and sandwich plates, J. of Composite Materials, 4:20-34.

Reddy, J.N., (1984). A simple higher order theory for laminated composite plates, ASME J. of Applied Mechanics, 51: 745–752.

Sayyad, A.S. and Ghugal, Y.M., (2012). Bending and free vibration analysis of thick isotropic plates by using exponential shear deformation theory, Applied and Computational Mechanics, 6:65–82.

Sayyad, A.S., (2013). Flexure of thick orthotropic plates by exponential shear deformation theory, Latin American Journal of Solids and Structures, 10:473-490.

Sayyad, A.S. and Ghugal, Y.M., (2013). Effect of stress concentration on laminated plates, J. of Mechanics, 29:241-252.

Sayyad, A.S. and Ghugal, Y.M., (2014a). A new shear and normal deformation theory for isotropic, transversely isotropic, laminated composite and sandwich plates, Int. J. of Mechanics and Materials in Design, 10:247–267.

Sayyad, A.S. and Ghugal, Y.M., (2014b). On the buckling of isotropic, transversely isotropic and laminated composite rectangular plates, Int. J. of Structural Stability and Dynamics, 14:1-32.

Sayyad, A.S. and Ghugal, Y.M., (2015). On the free vibration analysis of laminated composite and sandwich plates: A review of recent literature with some numerical results, Composite Structures, 129:177–201.

Shimpi, R.P. and Patel, H.G., (2006). A two variable refined plate theory for orthotropic plate analysis, Int. J. of Solids and Structures, 43:6783–6799.

Soldatos, K.P., (1992). A transverse shear deformation theory for homogeneous monoclinic plates, *Acta Mechanica*, 94:195–220.

Szilard, R. (2004). Theories and Applications of Plate Analysis: Classical, Numerical and Engineering Methods, New Jersey: John Wiley & Sons, Inc.

Thai, H.T. and Kim, S.E., (2010). Free vibration of laminated composite plates using two variable refined plate theory", Int. J. of Mechanical Sciences, 52:626–633.

Thai, H.T. and Kim, S.E., (2011). Levy-type solution for buckling analysis of orthotropic plates based on two variable refined plate theory, Composite Structures, 93:1738–1746.

Thai, H.T. and Kim, S.E., (2012). Analytical solution of a two variable refined plate theory for bending analysis of orthotropic Levy-type plates, Int. J. of Mechanical Sciences, 54:269–276.

Thai, H.T. and Vo, T.P., (2013). A new sinusoidal shear deformation theory for bending, buckling and vibration of functionally graded plates, Applied Mathematical Modelling, 37:3269-3281.

Touratier, M., (1991). An efficient standard plate theory, Int. J. of Engineering Sciences, 29:901–916.

Zenkour, A.M., (2006). Generalized shear deformation theory for bending analysis of functionally graded plates, Applied Mathematical Modelling, 30:67–84.

Zenkour, A.M., (2013). A simple four-unknown refined theory for bending analysis of functionally graded plates, Applied Mathematical Modelling, 37:9041–9051.